

BRL MR 2775

BRL

12
2.5

AD

AD A 043778

MEMORANDUM REPORT NO. 2775

BURNING RATES OF STANDARD ARMY PROPELLANTS
IN STRAND BURNER AND CLOSED CHAMBER TESTS

Bertram B. Grollman
Carl W. Nelson

August 1977

DDC
RECEIVED
SEP 7 1977
C

Approved for public release; distribution unlimited.

AD No. _____
DDC FILE COPY

USA ARMAMENT RESEARCH AND DEVELOPMENT COMMAND
USA BALLISTIC RESEARCH LABORATORY
ABERDEEN PROVING GROUND, MARYLAND

Destroy this report when it is no longer needed.
Do not return it to the originator.

Secondary distribution of this report by originating
or sponsoring activity is prohibited.

Additional copies of this report may be obtained
from the National Technical Information Service,
U.S. Department of Commerce, Springfield, Virginia
22151.

The findings in this report are not to be construed as
an official Department of the Army position, unless
so designated by other authorized documents.

*The use of trade names or manufacturers' names in this report
does not constitute endorsement of any commercial product.*

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER BRL MEMORANDUM REPORT NO. 2775	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) BURNING RATES OF STANDARD ARMY PROPELLANTS IN STRAND BURNER AND CLOSED CHAMBER TESTS.	5. TYPE OF REPORT & PERIOD COVERED MEMORANDUM REPORT	
7. AUTHOR(s) Bertram B./Grollman Carl W./Nelson	8. CONTRACT OR GRANT NUMBER(s)	
9. PERFORMING ORGANIZATION NAME AND ADDRESS U. S. Army Ballistic Research Laboratory Aberdeen Proving Ground, Maryland	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS 1T61102AH53	
11. CONTROLLING OFFICE NAME AND ADDRESS US Army Materiel Development & Readiness Command 5001 Eisenhower Avenue Alexandria, VA 22333	12. REPORT DATE AUGUST 1977	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) 34p.1	13. SECURITY CLASS. (of this report) UNCLASSIFIED	
15a. DECLASSIFICATION/DOWNGRADING SCHEDULE		
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited. BRL-MR-2775		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Burning Rate Propellant Closed Chamber Strand Burner		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) jmk Burning rate data determined over twenty years ago at the Ballistic Research Laboratory (BRL) and disseminated to only a limited audience have been referenced in several recent reports. This report provides a complete compilation of the experiments, the data, and the analyses to provide a usable reference for current investigations. It compares strand burner and closed chamber rates for the same propellant.		

(continued)

DO FORM 1 JAN 73 1473 EDITION OF 1 NOV 65 IS OBSOLETE

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

050 750

LE

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

Standard army gun propellants (M1, M2, M5, M6, M8, M10, and M17) were re-extruded into 3mm (1/8 in.) and 6mm (1/4 in.) strands for strand burner tests at pressures of 3.4 to 310 MPa (500 to 45,000 psi) and in closed chamber tests at densities of loading (Δ) of 0.089, 0.174, and 0.258 g/cc. Fifteen additional lots of standard propellants were tested in the closed chamber at densities of loading of 0.084 and 0.140 g/cc.

The report presents the raw data, method of calculation for burning rate, and coefficients for various burning rate equations. The report also proposes an empirical relationship between the propellant flame temperature and the burning rate parameters.

(DELTA)

TABLE OF CONTENTS

	Page
LIST OF ILLUSTRATIONS.	5
LIST OF TABLES.	7
I. INTRODUCTION.	9
II. DESCRIPTION OF EQUIPMENT	9
III. EXPERIMENT MAIN TEST	11
IV. RELATIONSHIPS OF THE COMBINED RESULTS.	11
V. PREVIOUS TEST IN CLOSED CHAMBER AT BRL	16
VI. BURNING RATE DATA FROM OTHER AGENCIES.	16
VII. CONCLUSIONS	31
REFERENCES	33
DISTRIBUTION LIST	35

LIST OF ILLUSTRATIONS

Figure		Page
1A	Correlation of Burning Rate Coefficient with Flame Temperature (English Units)	19
1B	Correlation of Burning Rate Coefficient with Flame Temperature (Metric Units)	20
2.	Burning Rate Comparison for M1.	22
3.	Burning Rate Comparison for M2.	23
4.	Burning Rate Comparison for M5.	24
5.	Burning Rate Comparison for M6.	25
6.	Burning Rate Comparison for M8.	26
7.	Burning Rate Comparison for M10	27
8.	Burning Rate Comparison for M17	28

Preceding Page Blank

LIST OF TABLES

	Page
I. Description of Standard Lots.	12
II. Burning Rate Results for BRL Extruded Propellants.	13
IIA. Propellant Burning Rate	14
III. High Pressure Strand Burner Data.	15
IV. Least Square Parameters for Various Burning Rate Equations Using Combined Strand Burner and Closed Chamber Results	
A English Units	17
B Metric Units	18
V. Description of Additional Closed Chamber Lots	21

Preceding Page BLANK

I. INTRODUCTION

"The chemical system of powder and gas presents a complex in which chemical reactions occur at high speed with remarkable precision. The free energy of powder gas is much less than that of powder, and the reaction between them, when once initiated, goes forward rapidly--in common parlance, the powder burns."¹

The National Defense Research Committee published in 1946 a summary of their investigation in interior ballistics in "Hypervelocity Guns and the Control of Gun Erosion."¹ The burning rate data for several propellants determined in closed chambers disagreed with test gun results. This was attributed to ignition problems and somewhat different formulations in the test propellants. R. H. Kent^{2,3} at Aberdeen proving Ground and BRL had studied the closed chamber data from 1925 on, and when a high pressure strand burner was acquired in 1950, suggested that the same propellants be used in both devices. These experiments were conducted and the results published in the monthly BRL Progress Reports (1953-1956) which had limited distribution. Standard army gun propellants (M1, M2, M5, M6, M8, M10, and M17) were re-extruded into 3mm (1/8 in.) and 6mm (1/4 in.) strands for strand burner tests at pressures of 3.4 to 310 MPa (500 to 45,000 psi) and in a closed chamber at densities of loading (Δ) of 0.089, 0.174, and 0.258 g/cc. Fifteen additional lots of standard propellants were tested in the closed chamber at densities of loading of 0.084 and 0.140 g/cc. Propellant description sheets are available for all the propellants.

This paper describes the experiments, the test data, and the derived burning rates. The results of tests at several other agencies are compared to those of the BRL standard tests.

II. DESCRIPTION OF EQUIPMENT

A. STRAND BURNER

The strand burner, used for the experimental firings, was manufactured by Autoclave Engineers and is capable of firing propellant samples at pressures up to 345 MPa (50,000 psi). The reaction chamber is 5.08 cm (2 in.) in internal diameter and 25.4 cm (10 in.) long. The auxiliary surge tank associated with the system has a capacity of 0.014m³ (0.5 ft.³).

¹F. C. Kracek, "Hypervelocity Guns and the Control of Gun Erosion," Part II Ballistics, Chapter 2, NDRC, Washington, D. C., 1946, pp. 21-53.

²R. H. Kent, "Report on Determination of Interior Ballistic Data by Closed Chamber Experiments in Connection with Project RB158," BRLR 32, Jan 1936.

³R. H. Kent, J. P. Vinti, "Cooling Corrections for Closed Chamber Firings," BRLR 281, Sep 1942. (AD #491852)

Preceding Page BLANK

The propellant samples fired varied in diameter from 0.25 cm (0.10 in.) to 0.64 cm (0.25 in.) and were about 15 cm (6 in.) long. They were inhibited by dipping in a vinyl resin solution. Each grain had four holes laterally drilled through it with a number 75 drill. In the first hole, a nichrome wire was inserted to ignite the grain. The other holes had 0.5 ohm fuse wire inserted through them to activate time interval recorders. The holes were drilled with the aid of a jig and, thus, the distances between holes were quite accurate. For fast burning propellants, 1.6 megacycle Potter counters were used; for slow burning propellants, Standard Electric 0.01 second clocks were used to measure the time intervals.

The nominal distance between two adjacent fuse wires was 5.08 cm (2 in.). Two time intervals were measured per round fired. The first time interval recorded was for the first 5.08 cm (2 in.) of burning and the second time interval was either for the second 5.08 cm (2 in.) or the whole 10.16 cm (4 in.) of burning.

The pressures were read from Bourdon gages. The scale divisions are 20 psi for the low range (0 to 3,000 psi), 500 psi for the middle range (0 to 15,000 psi) and 1,000 psi for the high range (0 to 50,000 psi). Because the system had slow leaks, it was over-pressurized and fired when it reached the desired pressure. While the grain was burning, the pressure increased slightly and was bled off into the surge tank. This surge was noticeable on the Bourdon gage only for very low initial pressures. The overall accuracy is estimated to be within 2%.

B. CLOSED CHAMBER

The closed chamber was manufactured by DuPont. It is capable of firing propellant samples up to pressures of 310 MPa (45,000 psi). The reaction chamber is 3.2 cm (1.25 in.) in diameter and about 6.6 cm (2.6 in.) long with a volume of 59 cc (3.6 in.³).

The propellant samples were fired as received, neither selected for uniformity nor inhibited. A gage plug containing a double piezo-electric gage and a gas release valve was screwed into one end of the chamber. An igniter plug with insulated leads was screwed into the other end. The leads were joined with 0.013 cm (0.005 in.) diameter tungsten wire, and the wire was wrapped with 0.25 g of thread propellant. The propellant charge was wrapped in a silk bag surrounding the igniter. Firing was initiated by applying 24 volts across the external igniter plug leads. Records were taken of the output of the double piezo-electric gage. One set of output leads was attached to a drum camera and a dual beam cathode ray oscilloscope to record pressure and rate of change of pressure versus time. The other set of output leads was attached to a Dumont No. 235 CRO to record pressure versus rate of change of pressure. The rates of change of pressure were obtained by electrically differentiating the pressure gage output.

III. EXPERIMENT MAIN TEST

The re-extruded standard propellants are described in Table I, including basic propellant lot and hexane densities.

For the strand burner test, both size cords were cut into 15 cm (6 in.) lengths and inhibited by dipping in a vinyl resin solution three times. The strands were burned at nine different pressures. The results are shown in Table II. For the smaller diameter grains, both the burning rates determined for the initial segment and the final segment of the seven sample propellants agreed within 2%, except for the M8 propellant at 207 MPa (30,000 psi) and 241 MPa (35,000 psi). The rates determined for the larger grains were somewhat slower than the rates determined for the corresponding smaller propellant grains. This was attributed to an increase in retained volatiles. Also, there were several failures due either to poor retention of coating or physical breakup during pressurization or burning. This series was fired during 1953-1954.

Several years after these tests, the Harwood High Pressure Strand Burner was transferred from the Bureau of Mines to BRL. During the proofing of the apparatus, the few remaining strands from the previous experiment were tested and the limited results are shown in Table III.

For the closed chamber test, the smaller size grains were cut into 5 cm (2 in.) lengths. Five, ten and fifteen gram charges were fired in duplicate for each propellant. The igniter was an 0.25 g thread propellant, having a diameter of 0.013 cm (0.005 in.). For the M1, M6, M10 and M17 samples, the ignitor was re-extruded from an M1 composition; for the M2 and M5 samples, the ignitor was re-extruded from an M2 composition; and for the M8 sample, the ignitor was re-extruded from an M8 composition. The pressure was measured with a stacked quartz piezo-electric gage mounted on a piston. This series of propellant samples was fired July 1954. The burning rates were calculated using the method reported in BRL Report 546, J. Wiegand⁴ and are tabulated in Table II. Table IIA contains the combined data and can be used for reference in English or Metric Units.

IV. RELATIONSHIPS OF THE COMBINED RESULTS

The burning rates determined in the strand burner and closed chamber were combined as shown in Table II and were used to fit the following expressions:

⁴J. H. Wiegand, "A Method for the Calculation of the Burning Rate of Powders from \dot{m}/dt Records for Closed Chambers," BRLR 546, May 1945.

Table I. Description of Standard Lots

Propellant.....	M1	M2	M5	M6	M8	M10	M17
Specification.....	JAN-P-309	JAN-P-323	JAN-P-323	JAN-P-309	JAN-P-381	PA-PD-123	MIL-PD-688A
Army Lot No.....	15529	302	4005	32412	9698	31831	6911
Nitrocellulose.....	85.00 83.54	77.45 75.08	81.95 80.93	87.00 85.74	52.15 52.35	98.00 97.93	22.00 22.30
% Nitrogen.....	13.15 13.13	13.25 13.23	13.25 13.23	13.15 13.14	13.25 13.22	13.15 13.16	13.15 13.20
Nitroglycerin.....	19.50 20.67	15.00 15.96			43.00 42.60		21.50 20.78
Barium Nitrate.....	1.40 1.36	1.40 1.45					
Potassium Nitrate.....	0.75 0.98	0.75 0.93			1.25 0.92		
Nitroguanidine.....							
Dinitrotoluene.....	10.00 (15.49)	0.96		10.00 (13.24)			54.70 54.97
Dibutylphthalate.....	5.00 0.97			3.00 1.02			
Diphenylamine.....	1.00 0.97	0.68	0.73	1.00 1.02	0.70	1.00 1.09	
Ethyl Centralite.....		0.60	0.60		0.60		1.50 1.68
Graphite.....		0.30 0.27	0.30 0.25			0.10	0.10
Ceylatic.....						0.10	0.30 0.27
Ethyl Alcohol.....	0.75 0.35	2.30 0.57	2.30 2.10	0.90 0.47	0.40	1.50 1.26	0.30 0.09
Water.....	0.50 0.31	0.70 0.36	0.70 0.43	0.50 0.52	0.18	0.50 0.91	0.10 0.00
Diethylphthalate.....					3.00 3.08		
Potassium Sulphate.....						1.00 0.98	
Isochric Flame Temp. ⁰ K, Tv. 2433		3372	3294	2583	3757	3034	2474
A Re-extruded Dia inches \pm .002	.121	.117	.119	.118	.118	.134	.121
Dimensional Density							
g/cc \pm .01	1.51	1.62	1.59	1.51	1.61	1.51	1.69
A Hexane Density	1.505	1.613	1.608	1.527	1.608	1.535	1.665
B	1.531	1.642	1.632	1.552	1.612	1.555	1.689
A BRL Lot No.	T466	T468	T470	T472	T474	T476	T478
B	T465	T467	T469	T471	T473	T475	T477
B Re-extruded Larger Diameter grains about .240 inches							

A .150 Die
B .250 Die

The first column for each propellant lists the specification values for the composition while the second is from the lot propellant description sheet

Table II. Burning Rate Results for BRL Extruded Standard Propellants
(Rates in./s)

Propellant	Test Run	5000	10,000	15,000	20,000	25,000	30,000	35,000	40,000	45,000	psi
T465 M1	SB		1.13	1.74	2.21		3.30				
467 M2	SB	1.65	3.14	4.48	5.48	6.67	7.96				
469 M5	SB	1.71	2.76	4.00	4.99	6.30	7.55	8.44	8.99	10.21	
471 M6	SB	.65	1.28	1.85	2.47	3.04	3.64	4.03	4.73	5.13	
473 M8	SB	2.10	3.75	5.57	6.76	7.56	9.30	10.52	11.28		
475 M10	SB	.90	1.61	2.33	3.27	4.00	4.50	5.20	5.82	6.57	
477 M17	SB		3.20*	7.00*	16.00*	20.00*					
T466 M1	SB	.59	1.17	1.68	2.26	2.89	3.36	4.10	4.59	5.12	
	cc-1	.65	1.19								
	cc-2	.65	1.19	1.82							
	cc-3	.69	1.19	1.72	2.29	2.89					
	SB-cc	.65	1.18	1.74	2.27	2.89	3.36	4.09	4.59	5.12	
T468 M2	SB	1.53	2.94	4.12	5.47	6.63	7.77	9.46	10.37	11.91	
	cc-1	1.34									
	cc-2	1.53	2.74	4.12	5.62						
	cc-3	1.72	2.82	4.12	5.33	6.51	7.73				
	SB-cc	1.53	2.83	4.12	5.48	6.54	7.75	9.46	10.37	11.91	
T470 M5	SB	1.41	2.78	3.99	5.47	6.67	7.92	8.43	9.95	11.86	
	cc-1	1.30									
	cc-2	1.46	2.55	3.73							
	cc-3	1.57	2.60	3.71	4.72	5.74	6.70				
	SB-cc	1.43	2.64	3.85	5.08	6.36	7.54	8.43	9.95	11.86	
T472 M6	SB	.68	1.31	1.91	2.53	3.13	3.97	4.50	5.05	5.51	
	cc-1	.72									
	cc-2	.66	1.24	1.97							
	cc-3	.85	1.54	2.13	2.81	3.52					
	SB-cc	.72	1.36	1.98	2.62	3.26	3.97	4.50	5.05	5.61	
T474 M8	SB	2.00	3.75	5.50	6.78	8.25			12.44	14.12	
	cc-1	1.86									
	cc-2	2.20	3.83	5.60							
	cc-3	2.15	3.59	5.31	6.84	8.39	9.90				
	SB-cc	2.04	3.73	5.47	6.80	8.31	9.90	11.30	12.44	14.12	
T476 M10	SB	.91	1.68	2.50	3.29	3.90	4.80	5.28	6.03	6.63	
	cc-1	.89									
	cc-2	.89	1.47	2.14							
	cc-3	1.02	1.59	2.19	2.87	3.54					
	SB-cc	.92	1.60	2.33	3.15	3.78	4.80	5.28	6.03	6.63	
T478 M17	SB	1.26	2.14	2.89	3.70	4.48	4.88	6.14	6.46	7.58	
	cc-1	1.16									
	cc-2	1.22	2.03	2.96							
	cc-3	1.07	1.93	2.63	3.32	4.01	5.30				
	SB-cc	1.20	2.06	2.82	3.70	4.48	5.09	6.14	6.46	7.58	

SB-cc - Average of all results
 SB Strand Burner
 * erratic results

Closed Chamber cc-1 = .089 g/cc
 Closed Chamber cc-2 = .174 g/cc
 Closed Chamber cc-3 = .258 g/cc

Table IIA. Propellant Burning Rate

MPa	psi	M1		M2		M5		M6		M8		M10		M17	
		mm/s	in./s	mm/s	in./s	mm/s	in./s	mm/s	in./s	mm/s	in./s	mm/s	in./s	mm/s	in./s
3.45	500	3.6	.14	7.4	.29	7.1	.28	3.0	.12	9.1	.36	5.1	.20	4.6	.18
10.34	1500	7.9	.31	14.7	.58	15.7	.62	8.1	.32	21.5	.84	10.9	.43	13.2	.52
20.69	3000	11.9	.47	23.9	.94	24.1	.95	12.7	.50	41.7	1.64	17.5	.69	20.8	.82
27.59	4000	13.7	.54	29.2	1.15	29.2	1.15	15.7	.62	45.7	1.80	19.8	.78	24.1	.95
34.48	5000	16.5	.65	34.9	1.33	34.3	1.43	18.3	.72	51.8	2.04	23.4	.92	30.5	1.20
68.97	10000	59.0	1.18	71.9	2.83	67.1	2.64	39.6	1.56	94.7	3.73	40.6	1.60	52.3	2.06
103.45	15000	44.2	1.74	104.6	4.12	97.8	3.85	50.3	1.98	138.9	5.47	59.2	2.33	71.6	2.82
157.93	20000	57.6	2.27	139.2	5.48	128.3	5.08	66.5	2.62	172.7	6.80	80.0	3.15	94.0	3.70
172.41	25000	73.4	2.89	167.4	6.59	161.5	6.36	82.8	3.26	211.1	8.31	96.0	3.78	113.8	4.48
209.60	30000	85.3	3.36	196.9	7.75	141.5	7.54	100.8	3.97	251.5	9.90	121.9	4.80	129.3	5.09
241.38	35000	103.9	4.09	240.5	9.47	214.1	8.43	114.3	4.50	287.0	11.50	134.1	5.28	156.0	6.14
275.86	40000	116.6	4.59	263.4	10.37	252.7	9.95	128.3	5.05	316.0	12.44	153.7	6.05	174.0	6.46
310.34	45000	130.0	5.12	302.5	11.91	301.2	11.86	142.5	5.61	358.6	14.12	168.4	6.63	192.5	7.58

Table III. High Pressure Strand Burner Data

Propellant	Pressure		Burning Rate Measured		Burning Rate Calculated	
	MPa	Ksi	mm/s	in./s	mm/s	in./s
T465 (M1)	379	55	149	5.88	155	6.12
	448	65	177	6.97	182	7.17
	544	79	212	8.33	219	8.63
	621	90	271	10.67	248	9.77
T466 (M1)	193	28	784	3.30	82	3.22
	276	40	121	4.76	115	4.52
	283	41	126	4.98	117	4.62
	379	55	165	6.50	155	6.12
	469	68	218	8.57	190	7.49
	586	85	282	11.11	235	9.26
T467 (M2)	172	25	145	5.70	171	6.74
	303	44	284	11.19	290	11.42
	434	63	381	15.00	406	15.97
	517	75	435	17.14	426	16.79
	579	84	476	18.75	531	20.89
T468 (M2)	138	20	132	5.21	139	5.48
	283	41	264	10.39	272	10.70
	414	60	368	14.50	386	15.21
	483	70	417	16.40	448	17.62
T470 (M5)	138	20	134	5.27	130	5.13
	283	41	257	10.12	257	10.13
	414	60	343	13.50	369	14.54
	414	60	353	13.90	369	14.54

*The burning rates were calculated using the bp^n equations in Table IV.

$r = a + bp^n$	or	$r = bp^n$
$a + bp$		bp
$a + bp^{.95}$		$bp^{.95}$
$a + bp^{.90}$		$bp^{.90}$
$a + bp^{.85}$		$bp^{.85}$
$a + bp^{.80}$		$bp^{.80}$

Some form of the equations cited above is often used in simplified interior ballistic calculation schemes. The least square fits of the above data to the various specific equations were computed. The results are tabulated in Tables IVA and IVB.

When the coefficients for the various experiments are plotted against the adiabatic flame temperature of the propellant (T) as shown in Figures 1A and 1B, it is seen that the lines cross the temperature axis at 1800K. This suggests an analytical expression for the coefficient b as a function of flame temperature and exponent as shown below:

$$b = (T - 1800) (1.65 \times 10^{-7}) (n^{-9.4}); r = \text{in./s}, p = \text{psi}$$

$$b = (T - 1800) (4.19 \times 10^{-7}) (145^n) (n^{-9.4}); r = \text{mm/s}, p = \text{MPa}$$

V. PREVIOUS TEST IN CLOSED CHAMBER AT BRL

A series of 15 lots of Army propellants were fired in a 181 cc Dupont Closed Chamber in 1951 at BRL. The chamber was 12 cm (4.72 in.) long and was 4.45 cm (1.75 in.) in diameter. The propellants were single perforated grains, 7-perforated grains and sheets of M1, M2, M6, M15 and M8 composition. These propellants are described in Table V.

Figures 2 through 8 compare these burning rates with the previously described re-extruded standards. The slight disagreement is attributed to small differences in composition. The data plotted on these figures include each of the standard propellants shown in Table II. The line shown is the least square fit of only the closed chamber data. The points within the square symbols are the best fit to the equation $r = bp^n$ for the combined data shown in Table IV. Since only the standard propellant data are available, the figures for the M5 and M10 propellants are presented for information only.

VI. BURNING RATE DATA FROM OTHER AGENCIES

I. During the first quarter of the 20th century, many European agencies conducted burning rate experiments which are summarized in Section 18 of

Table IVA. Least Square Parameters for Various Burning Rate Equations Using Combined Strand Burner and Closed Chamber Results

Standard Army Propellant Type		M1	M2	M5	M6	M8	M10	M17
$r = a + bp^n$	a	.122	.288	.475	-.048	.015	.082	.272
	b x 10 ⁴	.834	2.29	.838	2.87	11.5	2.38	3.38
	n	1.027	1.011	1.100	.924	.878	.955	.930
	c	.0158	.143	.373	.0167	.0815	.0721	.129
a+bp	a	.050	.242	.060	.129	.800	.19	.483
	b x 10 ⁴	1.131	2.572	2.515	1.247	2.968	1.458	1.563
	c	.0173	.145	.470	.056	.227	.080	.141
a+bp ^{.95}	a	-.062	-.013	-.189	.019	.499	.046	.278
	b x 10 ⁴	1.964	4.47	4.369	2.182	5.170	2.533	2.715
	c	.0250	.419	.548	.051	.134	.0702	.153
a+bp ^{.90}	a	-.187	-.298	-.467	-.116	.169	-.115	.155
	b x 10 ⁴	3.420	7.78	7.609	3.800	9.003	4.420	4.729
	c	.0429	.243	.706	.053	.089	.0738	.132
a+bp ^{.85}	a	-.447	-.89	-1.046	-.400	-.515	-.450	-.205
	b x 10 ⁴	6.153	14.00	13.69	6.836	16.199	7.94	8.51
	c	.0883	.471	1.020	.092	.249	.127	.198
a+bp ^{.80}	a	-.513	-1.042	-1.195	-.473	-.691	-.537	-.297
	b x 10 ⁴	10.54	23.97	23.44	11.70	27.736	13.59	14.57
	c	.0979	.505	1.103	.294	.161	.119	.185
bp ⁿ	b x 10 ⁴	1.90	5.316	4.293	2.20	12.00	3.46	9.41
	n	.951	.933	.948	.949	.874	.921	.836
	c	.0361	.152	.661	.027	.085	.076	.173
bp	b x 10 ⁴	1.146	2.68	2.648	1.280	3.226	1.518	1.715
	c	.212	.260	1.42	.068	1.447	.512	.608
bp ^{.95}	b x 10 ⁴	1.931	4.46	4.266	2.16	5.44	2.557	2.890
	c	.0448	.181	.617	.0185	.579	.0746	.334
bp ^{.90}	b x 10 ⁴	3.249	7.508	7.179	3.630	9.157	4.305	4.868
	c	.2305	.386	.982	.037	1.139	.094	.179
bp ^{.85}	b x 10 ⁴	5.461	12.62	12.06	6.102	15.402	7.238	8.189
	c	.4677	.904	1.73	.1311	.152	.220	.148
bp ^{.80}	b x 10 ⁴	9.347	21.27	20.32	10.282	25.961	12.195	13.805
	c	1.857	1.778	2.72	.309	.679	.467	.259

Units r in./s

a in./s
b in./s/(psi)ⁿ

$$c = \sum (r_c - r_e)^2$$

r_c = calculated
r_e = experimental

Table IVB. Least Square Parameters for Various Burning Rate Equations
Using Combined Strand Burner and Closed Chamber Results

Propellant Type		M1	M2	M5	M6	M8	M10	M17
$r = a + bp^n$	a	3.099	7.315	12.065	-1.219	.381	2.083	6.909
	b	.351	.891	.508	.724	2.308	.701	.879
	n	1.027	1.011	1.100	.924	.878	.955	.930
a+bp	a	1.270	6.147	1.524	3.276	20.320	4.826	12.268
	b	.417	.947	.926	.459	1.093	.537	.576
a+bp ^{.95}	a	-1.574	-3.302	-4.801	.482	12.675	1.168	7.061
	b	.564	1.284	1.255	.627	1.485	.727	.780
a+bp ^{.90}	a	-4.750	-7.569	-11.862	-2.946	4.292	-2.921	3.937
	b	.766	1.742	1.704	.851	2.016	.990	1.059
a+bp ^{.85}	a	-11.353	-22.606	-26.568	-10.160	-13.001	-11.430	-5.207
	b	1.074	2.444	2.390	1.193	2.828	1.386	1.486
a+bp ^{.80}	a	-13.030	-26.466	-30.353	-12.014	-17.551	-13.640	-7.544
	b	1.435	3.263	3.191	1.593	3.781	1.850	1.983
bp ⁿ	b	.548	1.403	1.221	.629	2.361	.860	1.532
	n	.951	.933	.948	.949	.874	.921	.836
bp	b	.422	.987	.975	.471	1.188	.559	.632
bp ^{.95}	b	.554	1.281	1.225	.620	1.562	.734	.830
bp ^{.9}	b	.727	1.681	1.607	.812	2.050	.964	1.090
bp ^{.85}	b	.953	2.203	2.105	1.065	2.689	1.264	1.430
bp ^{.80}	b	1.272	2.895	2.766	1.400	3.534	1.660	1.879

Units r mm/s
 a mm/s
 b mm/s/(MPa)ⁿ

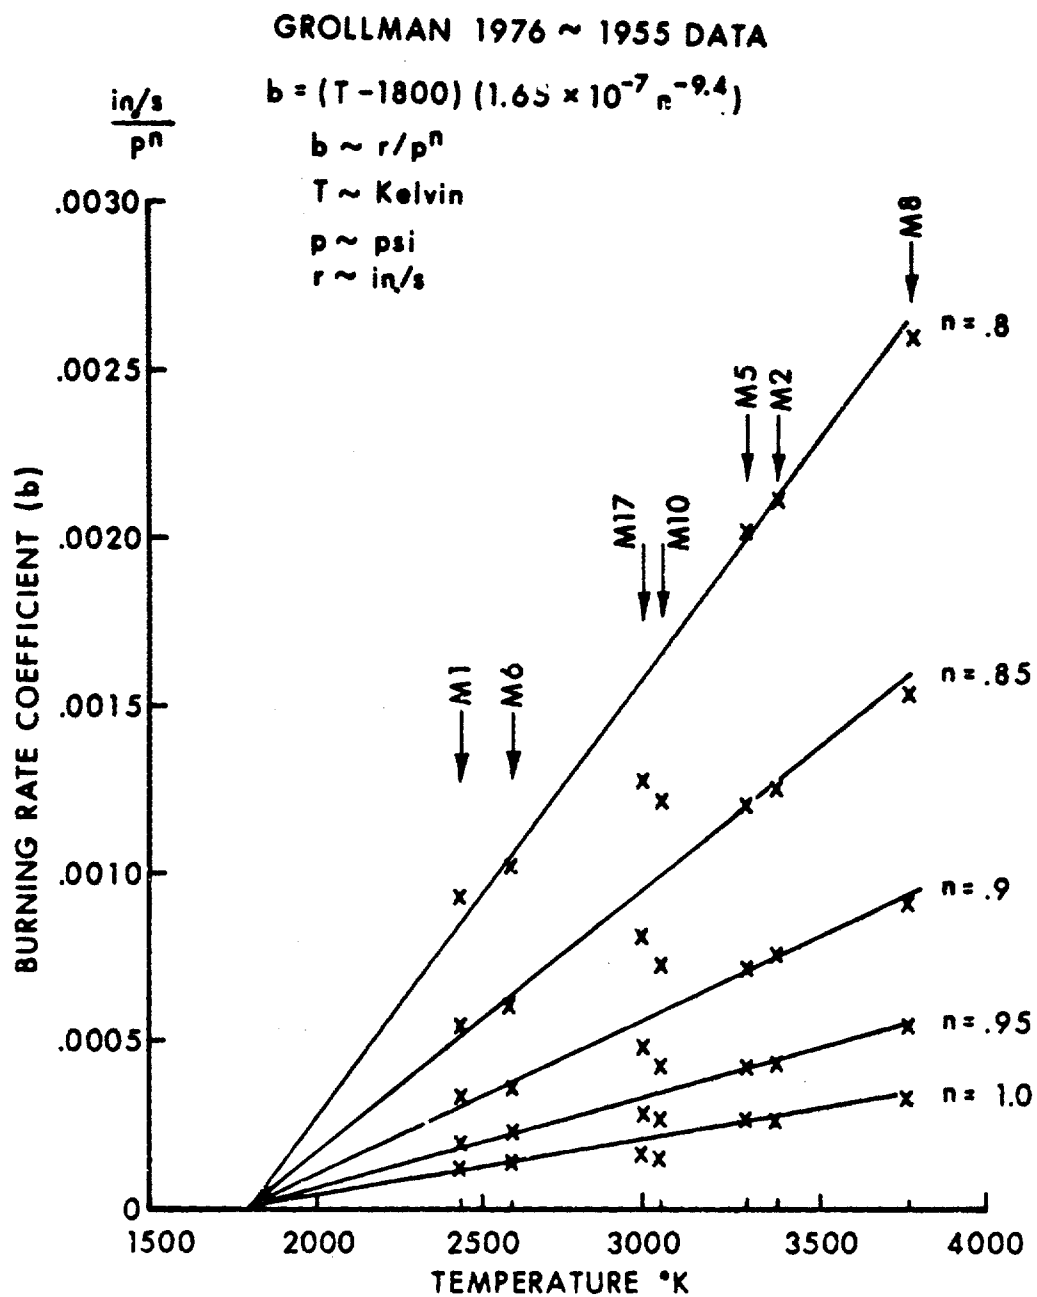


Figure 1A. Correlation of Burning Rate Coefficient with Flame Temperature

$$b = (T - 1800) (4.13 \times 10^{-6}) (145^n) n^{-9.4}$$

$$r = bp^n \quad r = \text{mm/s}$$

$$p = \text{MPa}$$

$$b = \frac{\text{mm/s}}{(\text{MPa})^n}$$

$$T = \text{Kelvin}$$

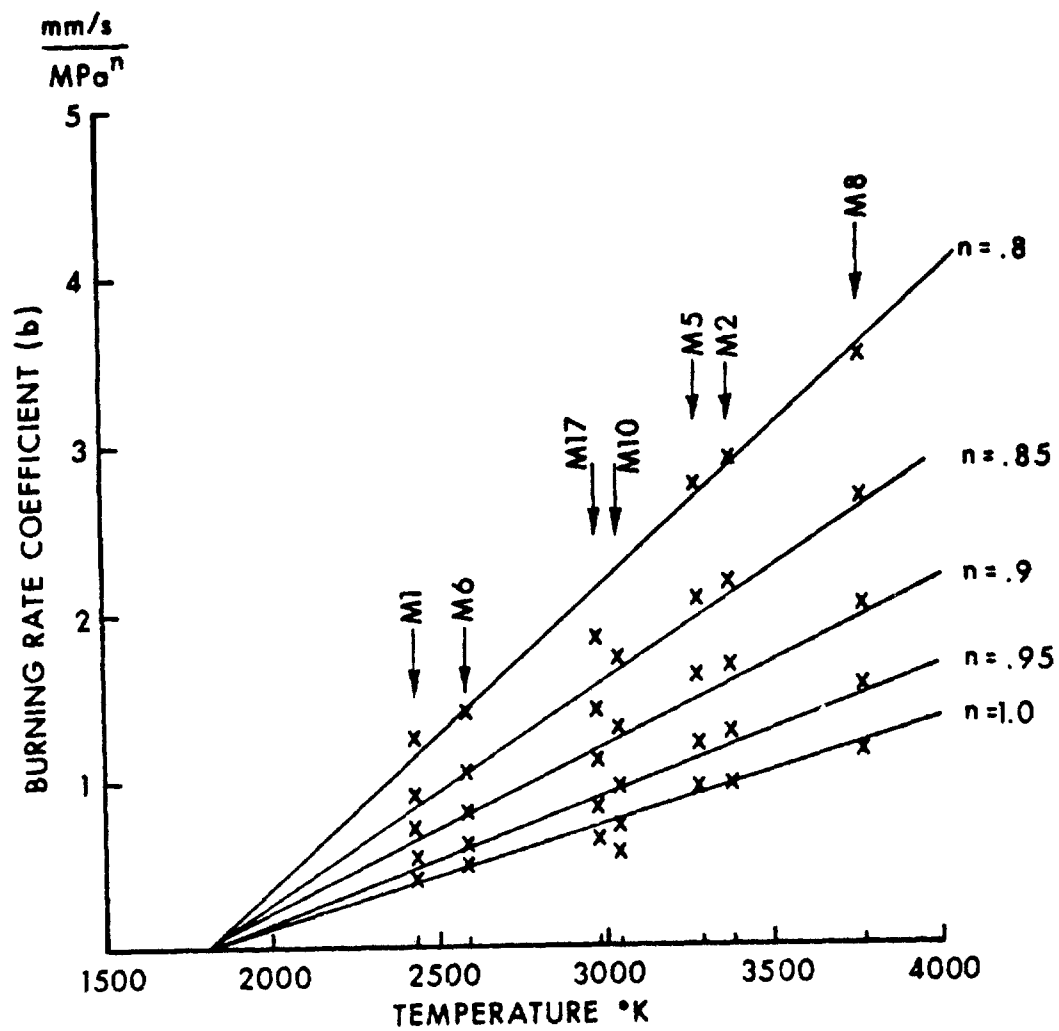


Figure 1B. Correlation of Burning Rate Coefficient with Flame Temperature

Table V. Description of Additional Closed Chamber Lots

Army Lot No.	X6658	10795	X5677	4258	302	5316	5280	19582	3727	X26526	14085	9407	16395	208	X1A4290
Propellant Type	MI	MI	MI	M2	M2	M2	M2	M2	M6	M6	M6	M6	M6	M6	MIS
Nitrocellulose	24.17	83.15	84.36	75.09	75.08	76.04	75.98	75.44	85.44	85.02	85.91	52.28	5226	51.85	20.10
Nitrogen	13.14	13.14	13.16	13.23	13.23	13.23	13.22	13.23	13.14	13.13	13.15	13.23	1324	13.21	13.15
Nitroglycerin				19.34	20.67	20.76	20.70	20.26				42.86	42.62	43.19	17.14
Barium Nitrate				1.37	1.36	1.47	1.44	1.40							
Potassium Nitrate				0.94	0.98	0.92	0.99	0.98				1.25	1.13	1.31	
Nitroguanidine															
Dinitrotoluene	(14.84)	(14.92)	(14.61)	1.06	0.96	(in MG)	(in MG)	.99	(12.97)	(13.83)	(13.04)				54.80
Dibutylphthalate	0.99	0.99	1.02	0.58	0.68	0.53	0.63	0.68	0.96	1.00	1.05	0.71	0.73	0.69	
Diphenylamine															
Ethyl Centralite				0.46	0.27	0.28	0.26	0.25							5.75
Graphite															.21
Cryolite															
Ethyl Alcohol	0.07	0.30	- 0.26	0.30	0.57	1.12	1.85	2.65	0.13	0.21	0.45	0.17	0.23	0.16	
Water	0.46	0.49	0.51	0.86	0.36	0.27	0.29	0.33	0.60	0.60	0.42	2.92	3.26	2.96	
Diethylphthalate															
Potassium Sulphate		0.94													
Manufacturer	EW	XW	LOW	HK	HA	HA	HA	HA	DuPont	DuPont	OOH	HR	HR	HR	DuPont
Date	1942	1943	1941	1941	1944	1942	1942	1940	1933	1948	1943	1944	1944	1944	1946
Length in.	.2828	.2790	.3617	.0472	.1290	.2500	.4320	1.1780	.0048	.3401	.5204	2.817	2.624	9.910	
Diameter in.	.0476	.0660	.1422	.0363	.0547	.0691	.2032	.5322	.0336	.1429	.2155	2.704	2.495	0.509	
Perforation Diameter in.	.0184	.0192	.0157	.0067	.0119	.0089	.0142	.0638	.0084	.0141	.0217	1.342	1.340		
Inner Web in.	.0146	.0234	.0230	.0148	.0214	.0301	.0403	.0838	.0126	.0244	.0368	.0202	.0255	.0463	.014
Outer Web in.															
Average Web in.															
Granulation	SP	SP	MP	SP	SP	SP	MP	MP	SP	MP	MP	Square	Square	Slab	Recutted

LOW Indiana Ord Works
 HA Hercules Radford
 OOH Oklahoma Ord Works
 HK Hercules Kenvil

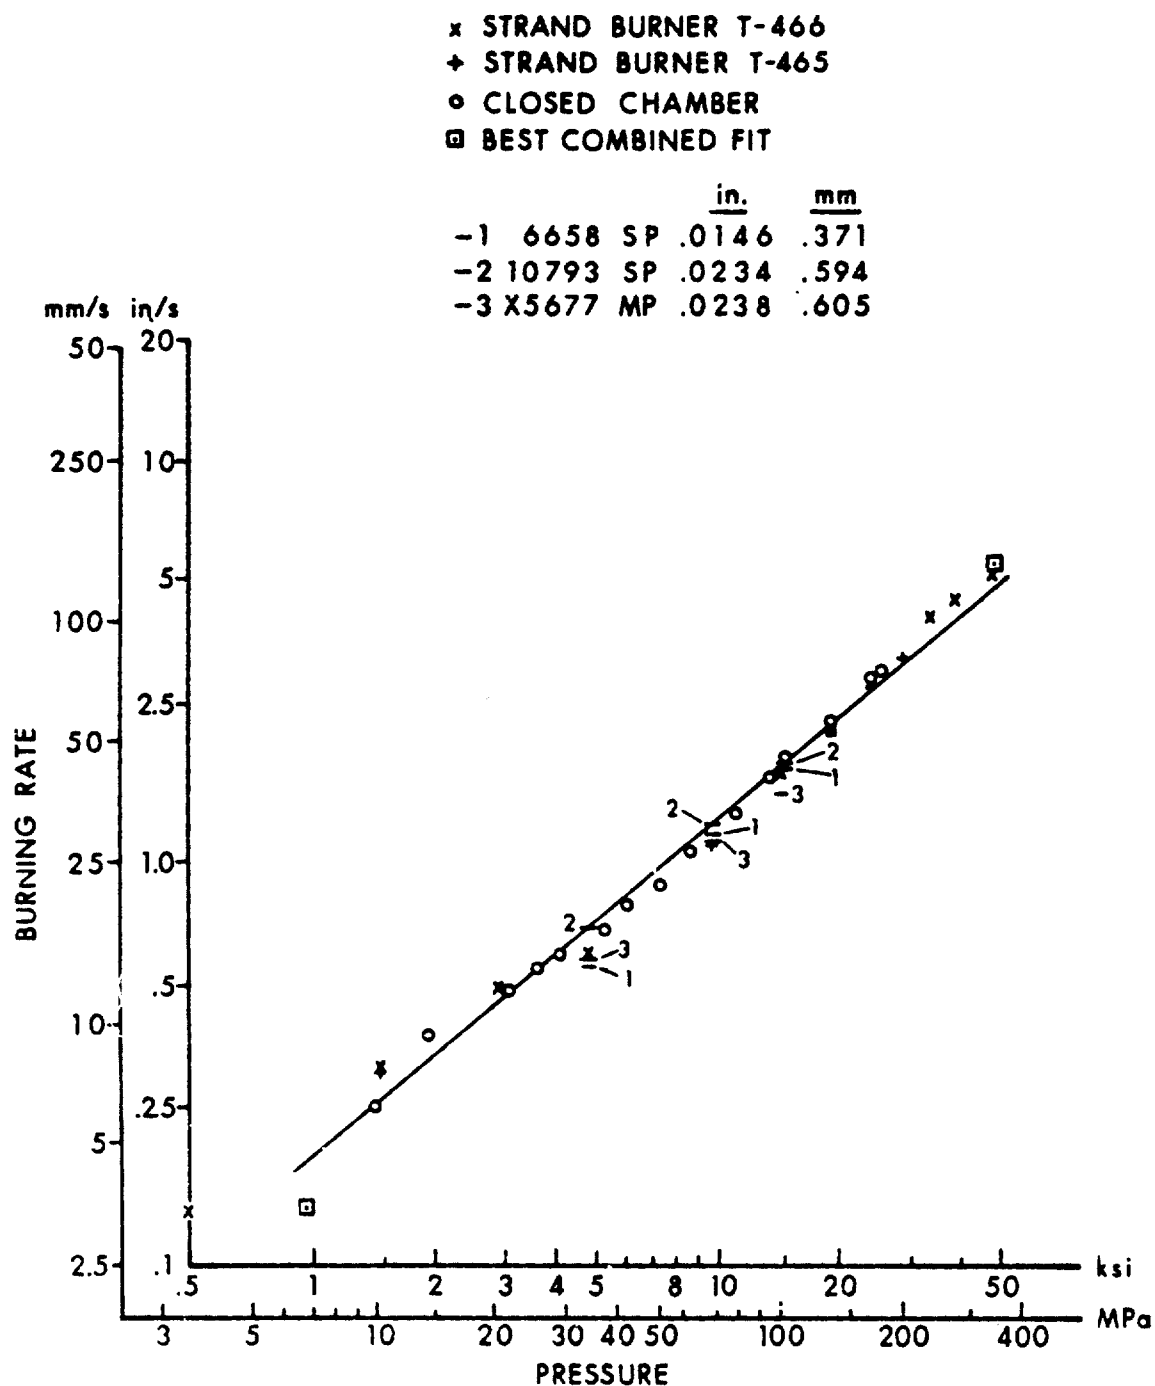


Figure 2. Burning Rate Comparison for M1

x STRAND BURNER T-468
 + STRAND BURNER T-467
 o CLOSED CHAMBER
 □ BEST COMBINED FIT

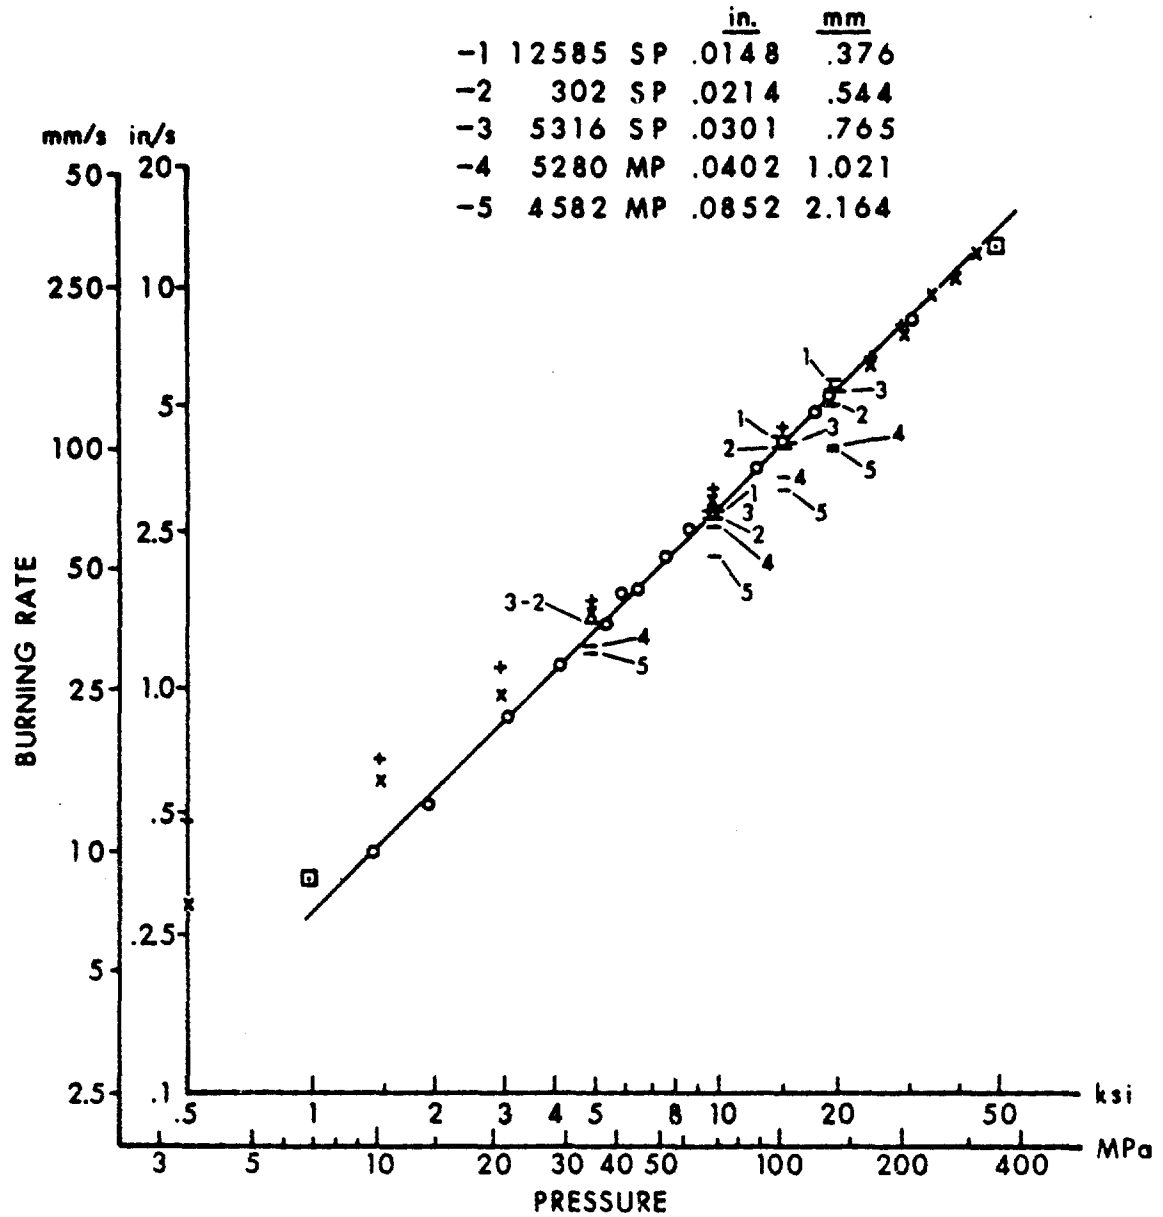


Figure 3. Burning Rate Comparison for M2

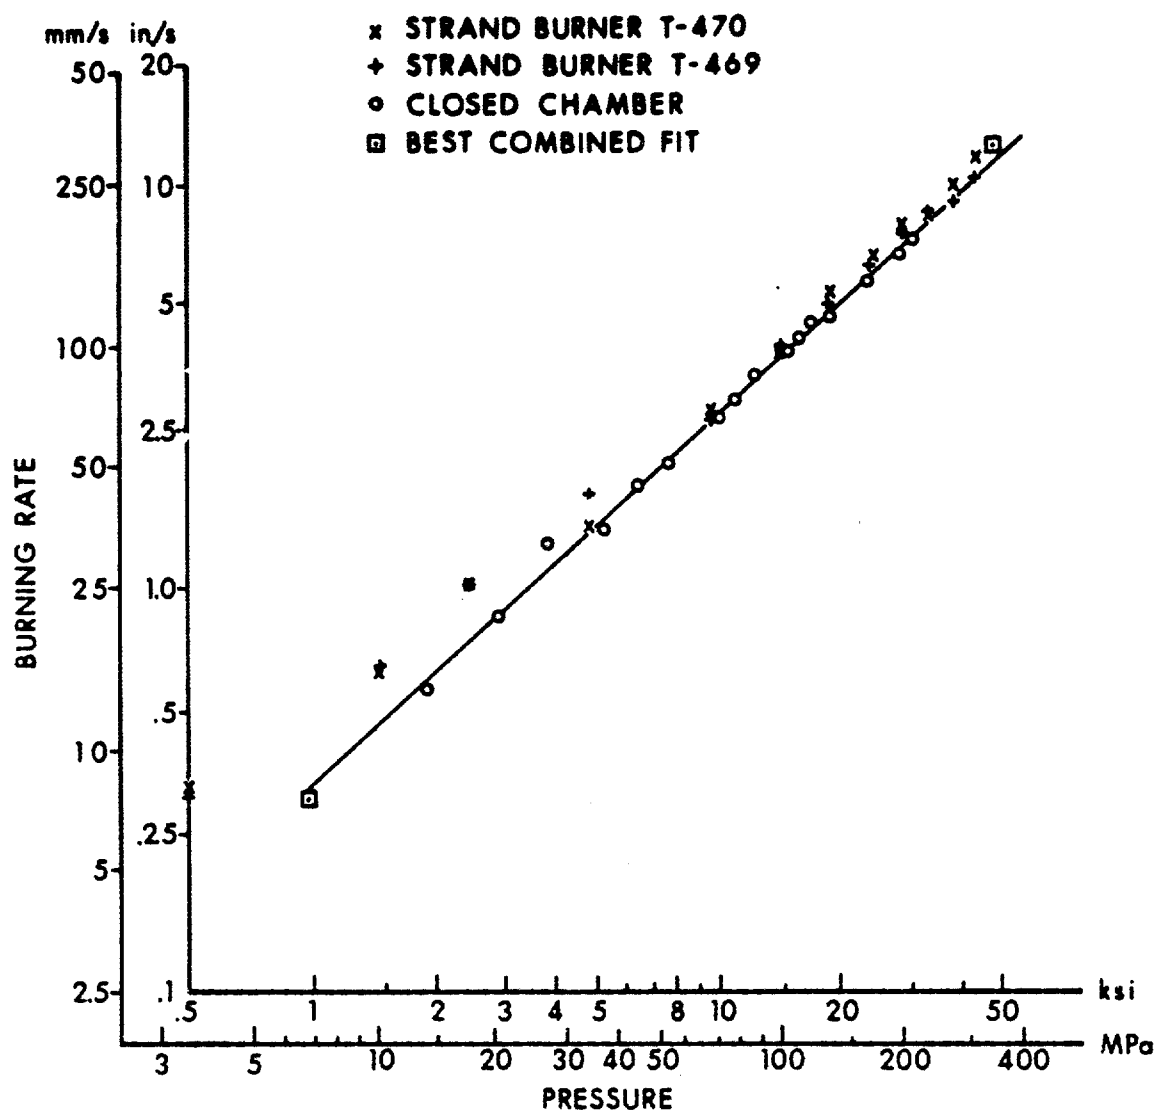


Figure 4. Burning Rate Comparison for M5

Figure 4. Burning Rate Comparison for M5

x STRAND BURNER T-472
 + STRAND BURNER T-471
 o CLOSED CHAMBER
 □ BEST COMBINED FIT

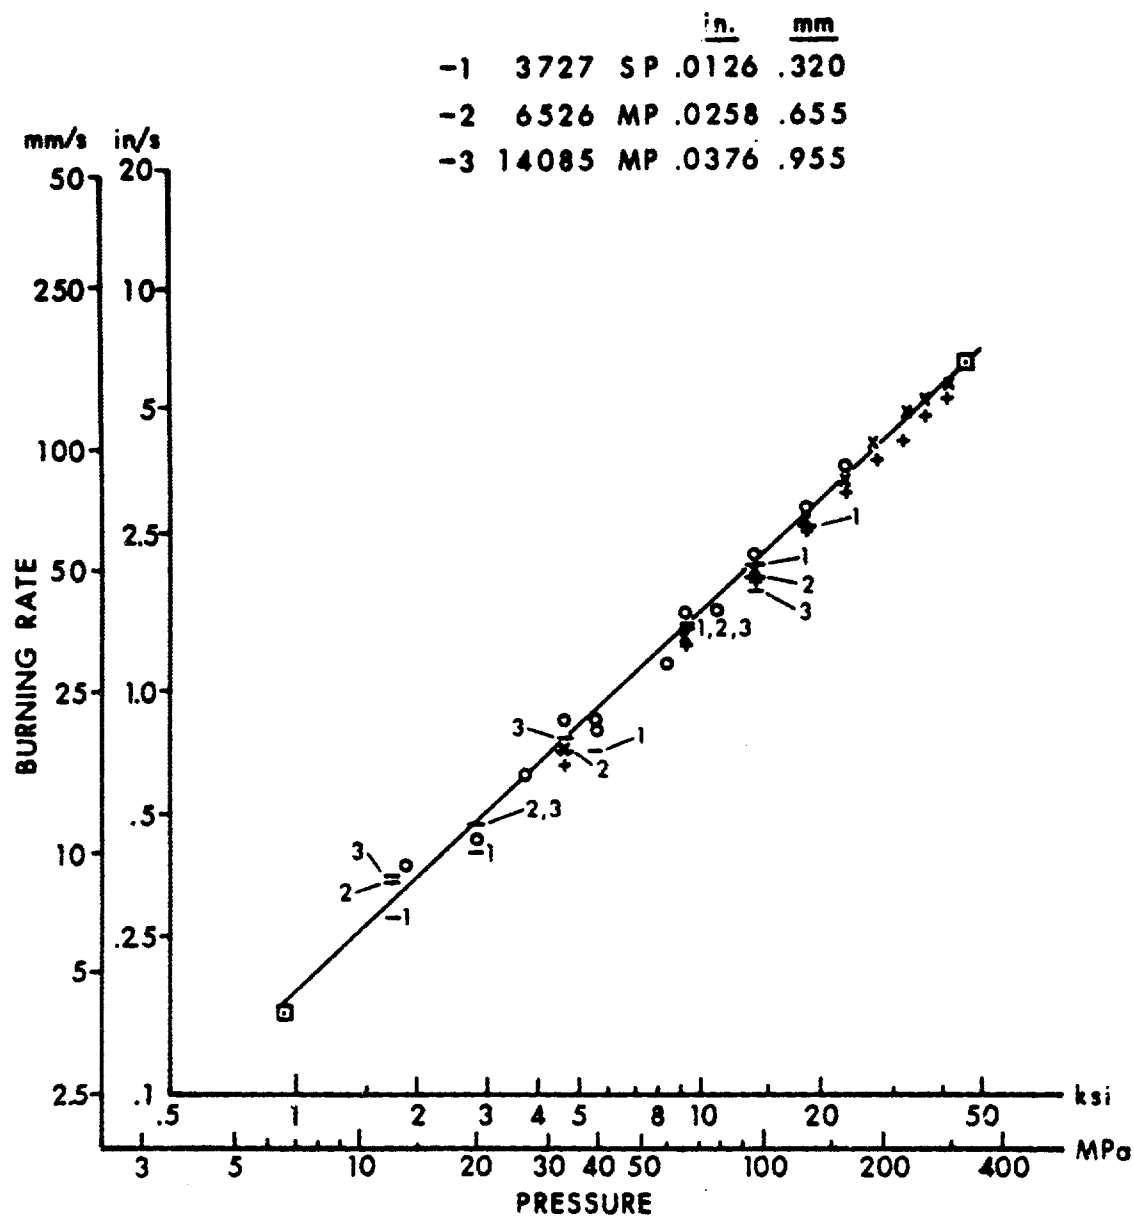


Figure 5. Burning Rate Comparison for M6

x STRAND BURNER T-474
 + STRAND BURNER T-473
 o CLOSED CHAMBER
 □ BEST COMBINED FIT

		in.	mm
-1	9697 SHEET	.0202	.513
-2	16395 SHEET	.0235	.597
-3	208 SHEET	.0463	1.176

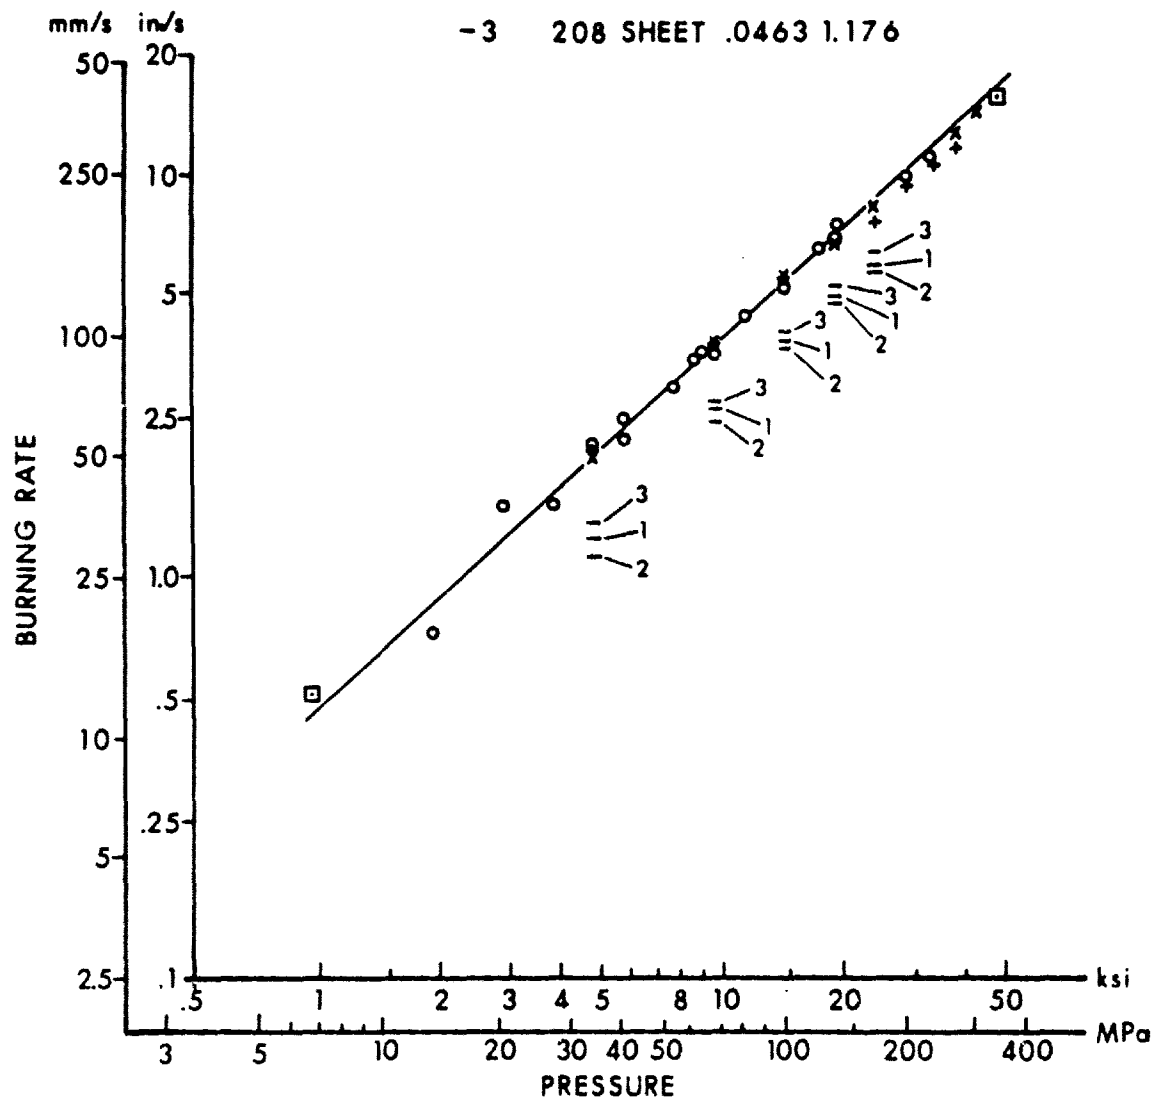


Figure 6. Burning Rate Comparison for M8

- x STRAND BURNER T-476
- + STRAND BURNER T-475
- o CLOSED CHAMBER
- BEST COMBINED FIT


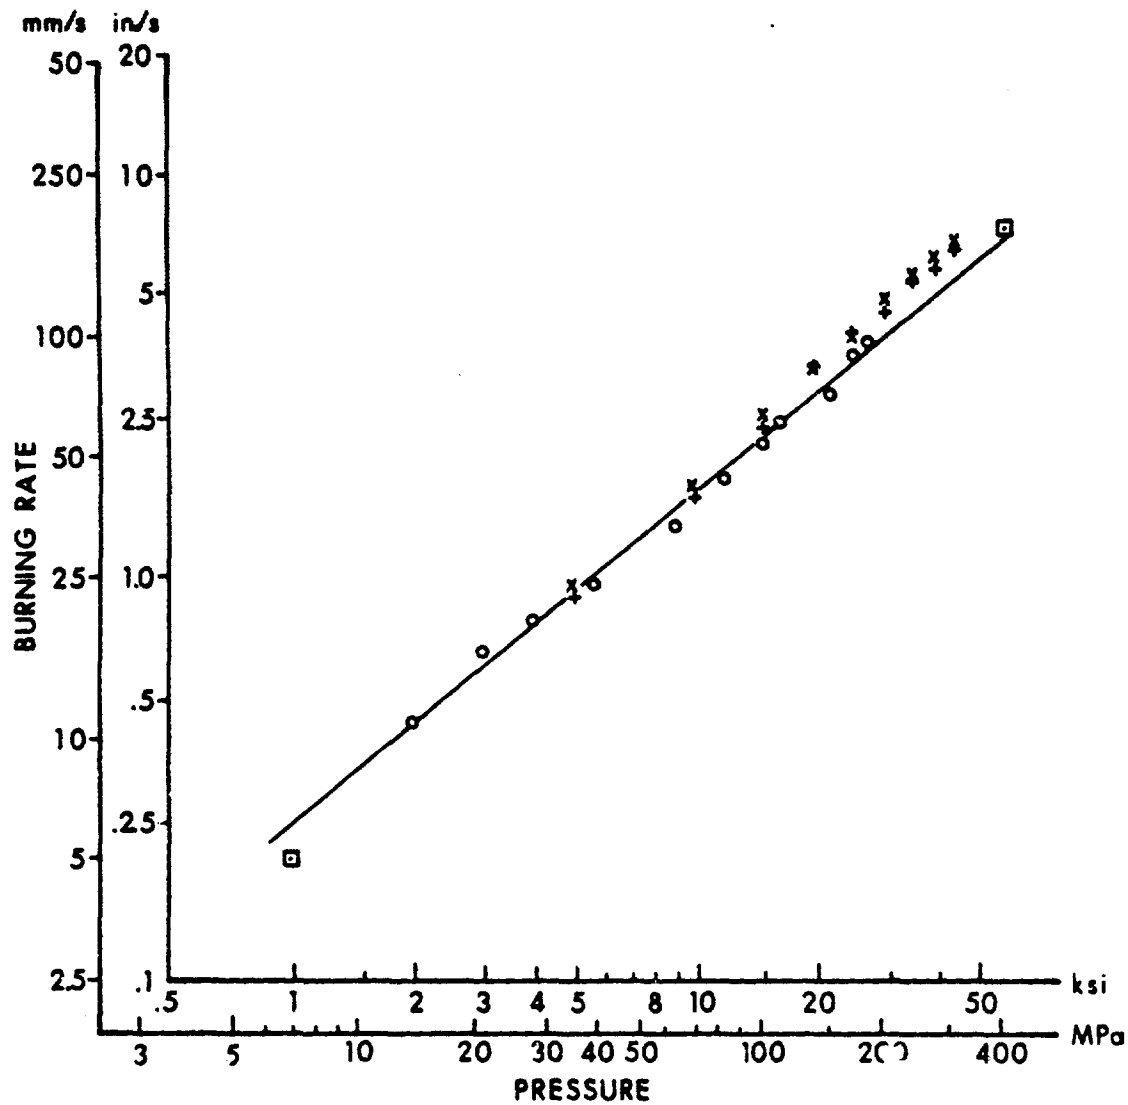


Figure 7. Burning Rate Comparison for M10

x STRAND BURNER T-478
 + STRAND BURNER T-477
 o CLOSED CHAMBER
 □ BEST COMBINED FIT

-1 6298 CORD $\frac{\text{in.}}{.014}$ $\frac{\text{mm}}{.36}$

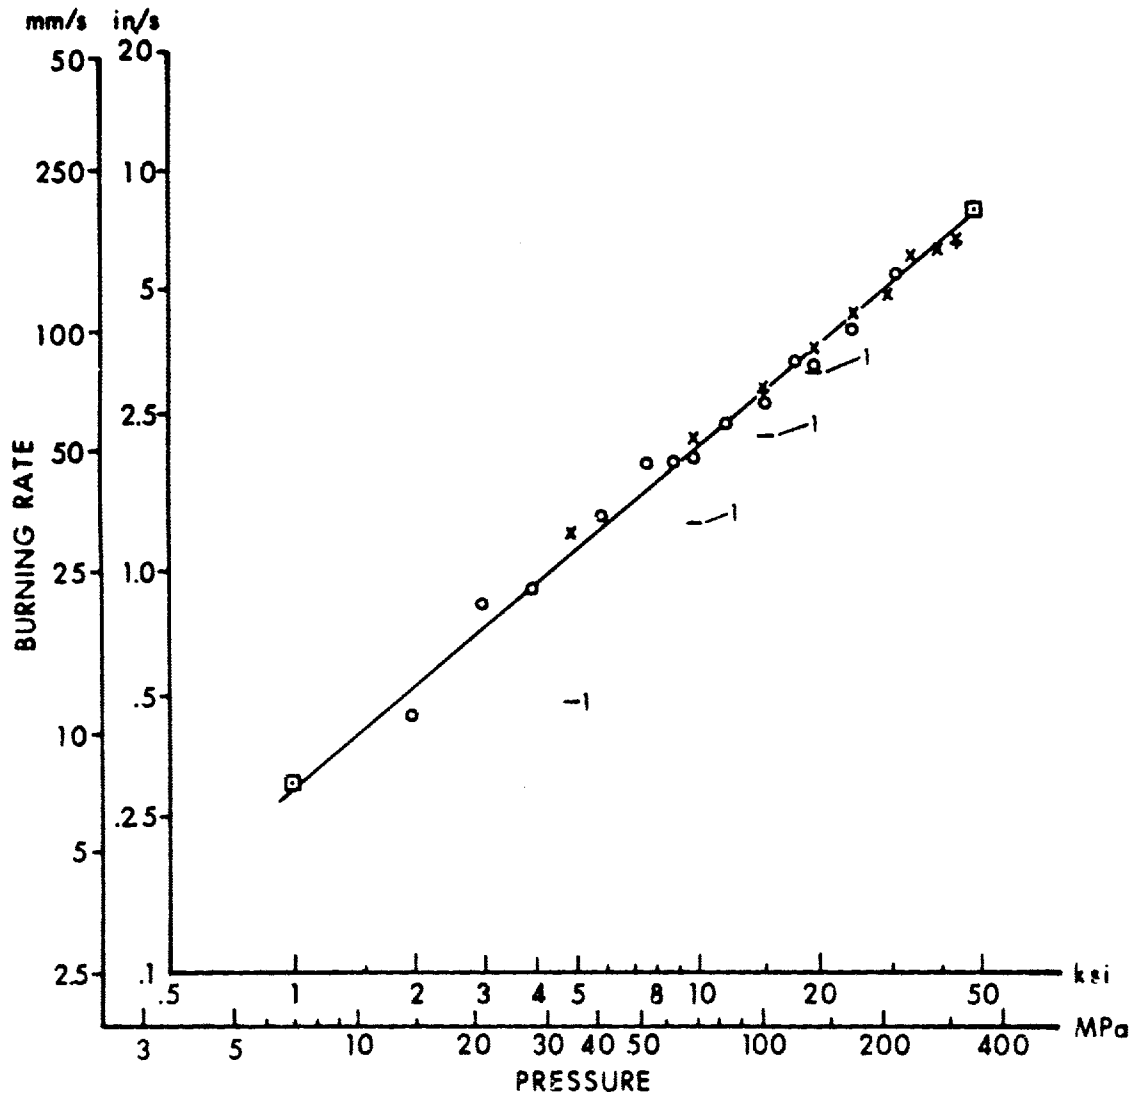

Cranz⁵, 1925. These rates for the NC propellant, which is similar to M1 propellant, were close to our measured values. In 1917, Col. Tschappat⁶ of the USA published the following:

The specific rate of combustion (k') is the regression normal to the surface of the propellant burning in its own gas at a pressure of one pound per square inch. It is proportional to the energy per pound of propellant (n') and is inversely proportional to the sum of the following:

(1) The energy required to heat a pound of propellant to the ignition temperature.

(2) The energy required to evaporate the water and alcohol from the propellant.

His equation (6) is

$$k' = \frac{.00000677n'}{87.5 (356^\circ\text{F} - \text{Temp of Prop}) + 8400 (\% \text{H}_2\text{O}) + 2980 (\% \text{alcohol})}$$

The value of k' agrees with our presented coefficient for M1.

He experimentally determined k' by placing several large grains in gun charges and measured the regressed distance in the recovered grains. His equation (9) was used to calculate the value of k' and it agreed for the several weapons tested. Then he determined the coefficients in the previous equation (6).

II. Geckler has a thorough treatment of combustion⁷. He tabulated the data of several investigators, and the results of Muraour are of particular interest. Both strand burner and closed chamber results are shown but unfortunately are not for identical propellants. The equations in section 2.4 relating the burning rate coefficients to the flame temperature of the propellants provide a very good fit to the data presented in Table II.

These equations are

$$r = 0.2 + 0.0000212e^{.709(T/1000)} p; r = \text{in./s}, p = \text{psi}$$

$$r = 5.0 + 0.078e^{.709(T/1000)} p; r = \text{mm/s}, p = \text{MPa}$$

⁵C. Cranz, "Lehrbuch der Ballistik," Bd II, Innere Ballistik, Springer, Berlin, 1926, translated NDRC, 1945.

⁶W. H. Tschappat, "Text Book of Ordnance and Gunnery," Wiley, New York, 1917.

⁷R. D. Geckler, "Selected Combustion Problems," AGARD, "The Mechanisms of Combustion of Solid Propellants," Butterworths, London 1954, pp. 289-299.

III. The composition of small arms propellants varies during burning as a result of the change in concentration of nitroglycerin (NG), nitrocellulose (NC) and the deterrent coating dibutylphthalate (DBP). As a consequence, BRL had a contract with Olin Corporation in 1974 to conduct closed chamber firings to provide⁸ burning rates for the interior ballistic prediction codes for small arms. The work included manufacturing 16 lots of propellant in two web sizes with 0 or 10% NG and with 0, 5, 10 and 15% DBP. Five samples of each propellant composition were burned in a closed chamber at a density of loading calculated to achieve a no heat loss maximum pressure of 180 MPa (26,000 psi). The smaller web for each propellant was also burned at 60% and 80% of the full charge. The raw data are reported as well as the calculated burning rates. Chemical analyses and thermochemical properties of all the propellants are tabulated in the Olin Corporation report.

The data for all the full charge firings were combined to obtain the linear burning rate constants as functions of propellant composition.

$$r = bp^n$$

$$\log_e r = \log_e b + n \log_e p$$

$$\log_e b = A_0 + A_1 (\% \text{ DBP}) + A_2 (\% \text{ NG}) + A_4 (\text{web})^2$$

$$n = n_0 + n_1 (\% \text{ DBP}) + n_2 (\% \text{ NG}) + n_3 (\text{web}) + n_4 (\text{web})^2$$

The web effect was very small and the following coefficients and exponents best fit the data:

	<u>r (in./s), p (psi)</u>	<u>r (mm/s), p (MPa)</u>
Constant Coefficient	$b = 9.833 \times 10^{-4}$	$b = 0.0250(145)^n$
	$n_0 = 0.83881$	0.83881
	$n_1 = 0.00581$	0.00581
	$n_2 = 0.00175$	0.00175
Constant Exponent	$A_0 = 6.61822$	0.62429
	$A_1 = -0.052882$	-0.052882
	$A_2 = 0.015907$	0.015907
	$n = 0.80530$	0.80530

⁸D. W. Riefler, "Linear Burn Rates of Ball Propellants Based on Closed Bomb Firings," BRL CR 172, Olin Corporation, Aug 1974. (AD #921704L)

The Olin constant exponent equation fits the BRL data very well; even though the BRL M8 composition has four times the NG content of that tested by Olin and the pressure levels were approximately twice that obtained by Olin.

VII. CONCLUSIONS

1. The burning rates calculated from strand burner and closed chamber data agree for identical propellants; however, the burning rates can be altered due to lot-to-lot variations in propellant ingredients.
2. The burning rate coefficient and exponent can be correlated to the calculated adiabatic flame temperature for the various types of propellant.
3. The burning rate coefficient and exponent are not independent.

REFERENCES

1. F. C. Kracek, "Hypervelocity Guns and the Control of Gun Erosion," Part II Ballistics, Chapter 2, NDRC, Washington, D. C., 1946, pp. 21-53.
2. R. H. Kent, "Report on Determination of Interior Ballistic Data by Closed Chamber Experiments in Connection with Project RB158," BRLR 32, Jan 1936.
3. R. H. Kent, J. P. Vinti, "Cooling Corrections for Closed Chamber Firings," BRLR 281, Sep 1942. (AD #491852)
4. J. H. Wiegand, "A Method for the Calculation of the Burning Rate of Powders from dp/dt Records for Closed Chambers," BRLR 546, May 1945.
5. C. Cranz, "Lehrbuch der Ballistik," Bd II, Innere Ballistik, Springer, Berlin, 1926, translated NDRC, 1945.
6. W. H. Tschappat, "Text Book of Ordnance and Gunnery," Wiley, New York, 1917.
7. R. D. Geckler, "Selected Combustion Problems," AGARD, "The Mechanisms of Combustion of Solid Propellants," Butterworths, London, 1954, pp. 289-299.
8. D. W. Riefler, "Linear Burn Rates of Ball Propellants Based on Closed Bomb Firings," BRL CR 172, Olin Corporation, Aug 1974. (AD #921704L)

Preceding Page BLANK

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
12	Commander Defense Documentation Center ATTN: DCC-TCA Cameron Station Alexandria, VA 22314	1	Commander US Army Missile Command ATTN: DRSMI-R Redstone Arsenal, AL 35809
1	Director Defense Advanced Research Projects Agency ATTN: C.R. Lehner 1400 Wilson Boulevard Arlington, VA 22209	1	Commander US Army Tank Automotive Development Command ATTN: DRDTA-RWL Warren, MI 48090
2	Director Institute for Defense Analyses ATTN: Dr. H. Wolfhard Mr. R.T. Oliver 400 Army-Navy Drive Arlington, VA 22202	2	Commander US Army Mobility Equipment Research & Development Command ATTN: Tech Doc Ctr, Bldg. 315 DRSME-RZT Ft. Belvoir, VA 22060
1	Commander US Army Materiel Development and Readiness Command ATTN: DRCDMA-ST 5001 Eisenhower Avenue Alexandria, VA 22333	1	Commander US Army Armament Materiel Readiness Command Rock Island, IL 61202
1	Commander US Army Aviation Systems Command ATTN: DRS AV-E 12th and Spruce Streets St. Louis, MO 63166	3	Commander US Army Frankford Arsenal ATTN: DRDAR-LCE-CI, Dr. J. Lannon SCA-CC, Mr. C. Dickey SCA-PP, Mr. L. Stiefel Philadelphia, PA 19137
1	Director US Army Air Mobility Research and Development Laboratory Ames Research Center Moffett Field, CA 94035	3	Commander US Army Armament Research and Development Command ATTN: DRDAR-LC, Dr. J.P. Picard DRDAR-LCE, Mr. C. Lenchitz DRDAR-LCE, Dr. R.F. Walker Dover, New Jersey 07801
1	Commander US Army Electronics Command ATTN: DRSEL-RD Ft. Monmouth, NJ 07703	1	Commander US Army White Sands Missile Range ATTN: STEWS-VT WSMR, NM 88002

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
1	Commander US Army Watervliet Arsenal ATTN: R. Thierry/Code SWEV-RD Watervliet, NY 12189	2	Commander US Naval Surface Weapons Center ATTN: S.J. Jacobs/Code 240 Code 730 Silver Spring, MD 20910
1	Commander US Army Harry Diamond Labs ATTN: DRXDO-TI 2800 Powder Mill Road Adelphi, MD 20783	1	Commander US Naval Surface Weapons Center ATTN: Tech Lib Dahlgren, VA 22338
1	Commander US Army Materials and Mechanics Research Center ATTN: DRXMR-ATL Watertown, MA 02172	1	Commander US Naval Underwater Systems Center Energy Conversion Department ATTN: R.S. Lazar/Code 5B331 Newport, RI 02840
1	Commander US Army Natick Research and Development Command ATTN: DRXRE, Dr. D. Sieling Natick, MA 01762	2	Commander US Naval Weapons Center ATTN: Dr. R. Derr Mr. C. Thelen China Lake, CA 93555
1	Director US Army TPADOC Systems Analysis Activity ATTN: ATAA-SA WSMR, NM 88002	1	Commander US Naval Research Laboratory ATTN: Code 6180 Washington, DC 20375
1	Commander US Army Research Office ATTN: Tech Lib P.O. Box 12211 Research Triangle Park, NC 27706	3	Superintendent US Naval Postgraduate School ATTN: Tech Lib Dr. David Netzer Dr. Allen Fuhs Monterey, CA 93940
1	Chief of Naval Research ATTN: Code 473 800 N. Quincy Street Arlington, VA 22217	2	Commander US Naval Ordnance Station ATTN: Dr. A. Roberts Tech Lib Indian Head, MD 20640
1	Commander US Naval Sea Systems Command ATTN: J.W. Murrin (NAVSEA-0331) National Center, Bldg. 2, Rm 6E08 Washington, DC 20360	2	AFOSR ATTN: J.F. Masi Dr. B.T. Wolfson Bolling AFB, DC 20332

DISTRIBUTION LIST

<u>No. of</u> <u>Copies</u>	<u>Organization</u>	<u>No. of</u> <u>Copies</u>	<u>Organization</u>
1	Pulsepower Systems, Inc. ATTN: L. C. Elmore 815 American Street San Carlos, CA 94070	1	TRW Systems Group ATTN: Dr. H. Korman One Space Park Redondo Beach, CA 90278
1	Science Applications, Inc. ATTN: Dr. R. B. Edelman 23146 Cumorah Crest Woodland Hills, CA 91364	2	United Technology Center ATTN: Dr. R. Brown Tech Lib P. O. Box 358 Sunnyvale, CA 94088
2	Rockwell International Corp Rocketdyne Division ATTN: Dr. C. Obert Dr. J. E. Flanagan 6633 Canoga Avenue Canoga Park, CA 91304	1	Universal Propulsion Co ATTN: H. J. McSpadden P. O. Box 546 Riverside, CA 92502
2	Rockwell International Corp Rocketdyne Division ATTN: Mr. W. Haymes Tech Lib McGregor, TX 76657	1	Battelle Memorial Institute ATTN: Tech Lib 505 King Avenue Columbus, OH 43201
1	Shock Hydrodynamics, Inc. ATTN: Dr. W. H. Anderson 4710-16 Vineland Avenue North Hollywood, CA 91602	1	Brigham Young University Dept of Chemical Engineering ATTN: Prof. R. Coates Provo, UT 84601
1	Thiokol Corporation Elkton Division ATTN: E. Sutton Elkton, MD 21921	1	California Institute of Tech Jet Propulsion Laboratory ATTN: Prof. F.E.C. Culick Pasadena, CA 91103
3	Thiokol Corporation Huntsville Division ATTN: Dr. D. Flanigan Dr. R. Glick Tech Lib Huntsville, AL 35807	1	Case Western Reserve Univ Division of Aerospace Sciences ATTN: Prof. J. Tien Cleveland, OH 44135
2	Thiokol Corporation Wasatch Division ATTN: Dr. John Peterson Tech Lib P. O. Box 524 Brigham City, UT 84302	3	Georgia Institute of Tech School of Aerospace Engineering ATTN: Prof. B. T. Zinn Prof. E. Price Prof. W. C. Strahle Atlanta, GA 30332

DISTRIBUTION LIST

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
1	Institute of Gas Technology ATTN: Dr. D. Gidaspo 3424 S. State Street Chicago, IL 60616	1	Rutgers State University Dept of Mechanical and Aerospace Engineering ATTN: Prof. S. Temkin University Heights Campus New Brunswick, NJ 08903
1	Johns Hopkins University Applied Physics Laboratory Chemical Propulsion Informa- tion Agency ATTN: Mr. T. Christian Johns Hopkins Road Laurel, MD 20810	1	Southwest Research Institute Fire Research Section ATTN: W. H. McLain P. O. Drawer 28510 San Antonio, TX 78228
1	Massachusetts Institute of Technology Dept of Mechanical Engineering ATTN: Prof. T. Toong Cambridge, MA 02139	1	Stanford Research Institute Propulsion Sciences Division ATTN: Tech Lib 333 Ravenswood Avenue Menlo Park, CA 94024
1	Pennsylvania State University Applied Research Lab ATTN: Dr. G. M. Faeth P. O. Box 30 State College, PA 16801	1	Stevens Institute of Technology Davidson Laboratory ATTN: Prof. R. McAlevy, III Hoboken, NJ 07030
1	Pennsylvania State University Dept of Mechanical Engineering ATTN: Prof. K. Kuo University Park, PA 16801	1	University of California, San Diego AMES Department ATTN: Prof. F. Williams P. O. Box 109 La Jolla, CA 92037
3	Princeton University Forrestal Campus Library ATTN: Prof. M. Summerfield Dr. L. Caveny Tech Lib P. O. Box 710 Princeton, NJ 08540	1	University of Illinois Dept of Aeronautical Engineering ATTN: Prof. H. Krier Transportation Bldg, Rm 105 Urbana, IL 61801
2	Purdue University School of Mechanical Engineering ATTN: Prof. J. Osborn Prof. S.N.B. Murthy TSPC Chaffee Hall West Lafayette, IN 47906	1	University of Minnesota Dept of Mechanical Engineering ATTN: Prof. E. Fletcher Minneapolis, MN 55455

DISTRIBUTION LIST

No. of
Copies

Organization

2 University of Utah
Dept of Chemical Engineering
ATTN: Prof. A. Baer
Prof. G. Flandro
Salt Lake City, UT 84112

Aberdeen Proving Ground

Marine Corps Ln Ofc
Dir, USAMSAA

DISTRIBUTION LIST

<u>No. of</u> <u>Copies</u>	<u>Organization</u>
2	University of Utah Dept of Chemical Engineering ATTN: Prof. A. Baer Prof. G. Flandro Salt Lake City, UT 84112

Aberdeen Proving Ground

Marine Corps Ln Ofc
Dir, USAMSAA